

Effects of Using “Nicoflok” Polymer on the Strength of Construction and Demolition Wastes

Hassan Ziary¹, Bahman Jafarie Nader^{2*}, Farzad Rezaie Moghaddam³

¹ Dept of Civil Engineering Professor, Iran Science and Technology university, Tehran, Iran

² Dept of Civil Engineering , Iran Science and Technology university, Tehran, Iran

Bahmanjafari93@gmail.com

³ Civil Engineering, University of Mohagheghe Ardebili, Ardebil, Iran

Abstract:

Construction and demolition wastes is always a trouble for construction and agriculture activities. In this study samples from bricks, cement mortar and gypsum and their composition which comes from building construction and demolition were collected. The effect of adding Nicoflok Mineral polymer (NMP) with cement was investigated on samples in the stabilized form. Thus the feasibility of increasing compressive and tensile strength and durability by stabilizing with 3, 6 and 12 percent cement and adding a mineral polymer which is known as Nicoflok with the amount of 10% of cement's weight for 7 and 28 days was investigated by collecting brick (burned clay), cement contained waste (waste of cement block workshop) and gypsum waste (passing from the sieve #40). The results showed that NMP generally increases compressive and tensile strength but the amount of increase depends on the material and the used mixture; samples with cement waste had more compressive strength in comparison with other samples, and samples with brick waste had the lowest strength. Adding 10% crushed gypsum to the mixture of brick and cement waste, improved the tensile strength in some cases. The results obtained from the compaction curve also showed that the materials including cement and block pieces have the highest compaction potential, while the materials including bricks have the lowest dry density.

Keywords:

Compressive and tensile Strength, Stabilizing, NMP, Portland Cement, C&D wastes

1. Introduction

To build new structures in dense urban areas, old structures are demolished and new buildings are built; these materials are called Demolition wastes. On the other hand, some of materials damage during transporting and building process, these materials are called construction wastes[1]; the sum of these materials are called construction and demolition (C&D) wastes. C&D wastes are always useless and commonly deposited in suburban areas which makes the environment polluted, diseases, etc, in addition to undesirable scenes. In a research conducted within the US strategic highway research program (SHRP), about 46 different ways of improving the soil quality were studied [2]. One of those was stabilization, stabilization is the modification of the physical and mechanical properties of the soil to achieve preset goals [3]. Additive use in stabilization can be divided into two groups of conventional materials such as cement, lime and tar, and new materials like silicates, mineral additives, enzymes, acids, salts, polymers and resins [4].

Leite et al (2011) divided the C&D wastes into 4 groups: cement materials, ceramic materials with high porosity, ceramic materials with low porosity and crushed stones [5]. Jain (2019) evaluated the potential of using C&D wastes in different parts of the building in economic and environmental conditions [6]. Arulrajah et al (2012) conducted grading, compaction, CBR and triaxial tests on the recycled concrete grains and compared their properties with the Sub-Base layer requirements [7]. Contreras et al (2016) substituted construction wastes for natural aggregates in bricks making and pressed by uniaxial hydraulic force and after 21 days of curing, they underwent a compressive strength test. The results showed a strength more than 4 MPa, which is higher than the standard required for brick production [8]. Ulugöl et al (2021) investigated the effect of using C&D wastes and glass by various temperatures and by various curing and also various Na concentrations. The compressive strength and micro structural investigation of these blends were evaluated. The results showed high strength of hollow bricks wastes in some cases [9]. Mousavi and karamvand (2017) investigated the potential of using nano polymer stabilizer called CBR Plus to stabilize

soft clay. The results showed an increase in the amount of CBR and compressive strength by using this polymer [10]. Cristelo et al (2018) investigated the using of fly ash on C&D wastes. The results showed an improvement in compressive strength and modulus of elasticity when using fly ash after 28 days of curing at ambient temperature and relative humidity [11]. Arulrajah et al (2021) investigated the use of polyethylene terephthalate (PET) and C&D wastes as a substitute to traditional materials. For this purpose, different proportion of materials were combined. The results showed all the geo polymer-stabilized blends using 5% fly ash + 5% slag and 10% slag satisfied the minimum UCS limit [12]. Gobieanandh and Jayakoya (2016) tested the wastes in a region in Sri Lanka. In this investigation, construction waste was mixed with different proportions of natural materials and stabilized samples with cement were made and then they undergo compaction and CBR tests[13]. Cement as a cohesive material is used to stick gravel, sand and other materials [14]. Ibrahim et al (2020) investigated the possibility of using concrete with recycled concrete aggregate (RCA) and with recycled fine aggregate (RFA) [15]. Parmenevich and Vladmirovich (2013) evaluated the effect of adding three stabilizers with the names “ANT”, “Nano-STAB” and “NMP” on the materials made of different percent of sand and crushed stone. The results show an increase in compressive and tensile strength for 5 and 7 day samples in the case of using “NMP”. They chose 10% of cement’s weight for the amount of “NMP” [16]. Gosev and Nekhoroshkov (2013) stated the results of using the powder of NMP for improving compressive and tensile strength of the materials used in road construction as: for Dobrbolyo street in 2010, compressive and tensile strength of asphalt grains with 5% cement and 0.5% NMP were 6.5 and 1.25 MPa respectively; for a street in Suchi area in 2010, compressive and tensile strength for crushed materials with 5% cement and 0.5% NMP were 7.7 and 1.1 MPa, respectively; for Velam area in 2010, for the surface of the sieved granite grain pavement which was stabilized with 6% cement and 0.6% NMP, compressive and tensile strength were 6.9 and 0.9 MPa respectively [17]. Rezaie moghaddam et al (2020) evaluated the effect of adding NMP and cement as stabilizer on coastal and desert sands. In this research compacted samples with 3, 6 and 12 percent of cement and 10 weight percent of cement with NMP were made. The results showed that the samples which have NMP polymer have 7 and 28 days compressive and tensile strength more than the samples without NMP

polymer. Also, NMP stabilized samples have more Durability than other samples [18]. Gavrilina & Bonder (2018) have performed uniaxial compressive strength on samples with cement and NMP. The results of this study showed that adding NMP increases the compressive and bending strength of samples by 20%. The amount of NMP in this study is 8-10 percent [19]. Moradi et al (2021) conducted a research to investigate and compare the effect of chemical and biological stabilizers on clay subgrade soil. For chemical stabilization polymers called cationic polyelectrolyte (CPE) and NMP were used. The results showed an increase in soil compressive strength and resilient modulus (*MR*) due to use of NMP polymer [20]. Zirrak baroughi et al (2020) evaluated the effect of using NMP and cement on granular soils and recycled asphalt materials (RAP). In this research the optimal value of NMP for use in the samples is 0.9 percent. Also, the use of this type of polymer has improved the resistance conditions in different layers of pavement [21].

In this study, the possibility of using (C&D) materials with cement and Nicoflok, which is a mineral polymer powder and has been imported from Russia, as a stabilization way in roads construction was investigated. In this way the environmental pollution will decrease. In addition, the use of materials which are extracted from mines and consequently the cost will decrease significantly.

2. Experimental Study

2-1- Materials

The materials used in this study include cement, water, NMP and C&D wastes. The properties of each of these materials are as follows:

2-1-1- Cement

The cement used in this study is type II pozzolan cement which was produced in Ardebil cement co. Density of this cement is 3130 kg/m³. The results of XRF test on the sample of cement are given in Table 1.

Table 1. XRF test results on Cement materials

Element	SiO ₂	Al ₂ O ₃	Fe ₂ O ₃	CaO	K ₂ O	Na ₂ O	SO ₃	CL
Wt%	26.85	6.5	3.2	56.5	1.1	44	<1	<5

2-1-2- Water

The water used in this research is the beverage water of Ardebil City. In most mix design schemes, beverage water is the adequate one for the mix [22]. the compounds in the water used in making the samples are presented in Table 2.

Table 2. the results of physical and chemical of water in the Ardabil city [23]

Indicator	Minimum	Maximum	Average
pH	6.82	8.41	7.38
Turbidity (NTU)	0.21	1.1	0.05
Carbonate (mg/lit)	0	27	1.09
Nitrate (mg/lit)	15.5	36	27.9
Sulphate (mg/lit)	23	525	245.3
Phosphate (mg/lit)	0.07	0.36	0.234
Colorine (mg/lit)	25	215	132.4
Total Hardness (mg/lit)	47	770	663

2-1-3- NMP Polymer

NMP additive is produced in the north of Russia according to TU5743–003–13881083–2006 Standard. This ash-like material has 800-1200 kg/m³ density and less than 2% moisture. Also more than 90% of it passes through 0.315 mm sieve. This material is not toxic, flammable and dangerous and has a hygienic certificate. It can be transported and stored in low temperatures and keeps its properties in temperatures lower than 40-50° C. It is a hydrophobic material and should not have direct contact with water during the storage. Fig. 1 shows NMP.



Fig. 1. NMP materials

To recognize the ingredients, XRF test was conducted by PW 1480 machine and IQ+ software in Iran University Science and Technology (IUST) central laboratory according to ASTM E1621[24]. The results are shown in Table 3.

Table 3. XRF test results on NMP polymer

Element	Na ₂ O	MgO	Al ₂ O ₃	SiO ₂	P ₂ O ₅	SO ₃	K ₂ O	CaO	TiO ₂
Wt%	2.930	0.735	0.786	48.046	0.118	2.969	0.505	33.134	<<
Element	V ₂ O ₅	Cr	Mn	Fe ₂ O ₃	Ni	ZnO	Sr	Y ₂ O ₃	PbO
Wt%	-	-	<<	0.775	<<	-	<<	-	-
Element	Ba	ZrO ₂	Cl	CO	Ce	MO	F	Cu	L.O.I
Wt%	-	-	-	-	-	-	4.083	<<	5.911

As it is shown in Table 3, all ingredients are the same as cement ingredients, except CL and MgO, but the proportions of ingredients are different. Silicon Oxide is one the stick agents in cement and its high percent in NMP materials, makes the mix more adhesive.

2-1-4- Aggregate

The used aggregates were classified into three groups: the first group pertains to wastes which contain cement mortar grains collected from cement block workshops in Ardebil; second group is brick waste (burned clay) which was collected from brick stores; third group is gypsum waste. The first and second group materials has dimensions less than 1 inch and the third group materials were crushed with labor force and passes through #40 sieve.

2-2- Conducted Testes on the Materials

In this study, the grading of aggregates was done according to Iran Highway Asphalt paving code No. 234 [25]. The materials were divided into 4 main groups (A, B, C, D) according to the type of their components, then to perform the tests of each of these groups, according to the percentage of cement and polymer, they were divided into sub-branches 1 to 6, as follows: Groups 1 to 3 only have the mentioned percentages of cement and no polymer, and subgroups 4 to 6 have polymer in addition to the percentages of primary cement

to determine the effect of the polymer at a ratio of 10 percent by weight of the primary cement, as shown in Table 4. Standard Proctor-compaction test was conducted on them to determine optimum moisture content. This content of moisture was used to make stabilized samples with cement and NMP. The 7 and 28 day samples undergo compressive strength and indirect tensile tests. Also some samples undergo 45 cycles of freezing and thawing test according ASTM C666 [26]. On these samples and control samples, compressive strength test was conducted to evaluate the effect of NMP during freeze-thaw. A total of 380 samples were made. For each percent of cement and NMP, 6 samples for compressive strength, 6 samples for indirect tensile and 3 samples for durability test were made. To calculate the optimum moisture content for each group, 5 samples with different percent of water were made and undergo proctor-compaction test.

Table 4. Classification of C&D wastes

Type of materials	Materials percent			Mix design name	Cement percent	NMP percent
	Cement wastes	Brick wastes	Gypsum wastes			
Group A	100	0	0	A-1	3	0
	100	0	0	A-2	6	0
	100	0	0	A-3	12	0
	100	0	0	A-4	3	0.3
	100	0	0	A-5	6	0.6
	100	0	0	A-6	12	1.2
Group B	0	100	0	B-1	3	0
	0	100	0	B-2	6	0
	0	100	0	B-3	12	0
	0	100	0	B-4	3	0.3
	0	100	0	B-5	6	0.6
	0	100	0	B-6	12	1.2
Group C	50	50	0	C-1	3	0
	50	50	0	C-2	6	0
	50	50	0	C-3	12	0
	50	50	0	C-4	3	0.3
	50	50	0	C-5	6	0.6

	50	50	0	C-6	12	1.2
Group D	45	45	10	D-1	3	0
	45	45	10	D-2	6	0
	45	45	10	D-3	12	0
	45	45	10	D-4	3	0.3
	45	45	10	D-5	6	0.6
	45	45	10	D-6	12	1.2

2-2-1- Curing of Samples

The samples for 7 and 28 day compressive tests were kept in plastic bags for 24 hours after mixing to get cured in optimum moisture. Then until the time of testing, they were kept inside the sand and sprayed on the surface. It was done daily. The samples for freeze-thaw test were kept in water basin for 14 days and then undergo freeze-thaw test. Control samples for freezing and thawing test were kept in water until test.

2-2-2- Grading

According to NMP producer, we should use aggregates lower than 1 inch. According to Iran Highway Asphalt Paving Code No.234 one group for base which has been named “IV” is appropriate. The grading curve is shown in Fig. 2.

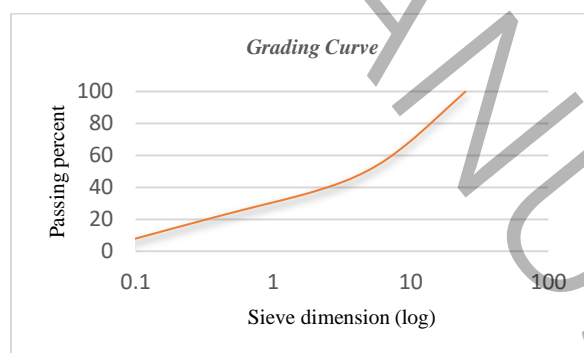


Fig. 2. Grading curve

2-2-3- Proctor – Compaction Test

Proctor-compaction test was conducted on each of 4 groups of materials according ASTM D558 [27]. The grading curve for materials is shown in Fig. 3. The moisture content for A, B, C and D was 6.5, 8.5, 8 and 13.5 percent respectively. As it is seen, the moisture content of group C is between moisture contents of A

and B, because this group is made by mixing groups A and B. Also the presence of gypsum in group D leads in more water absorption and increase the optimum moisture content. As can be seen, group A has a considerable dry density compared to other groups, the reason for the high density of these materials is the texture of the aggregates and the existence of the primary granulation of these materials, which is used in the production of building blocks.

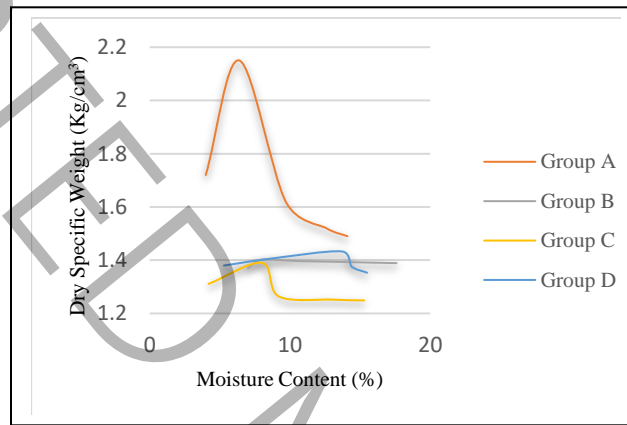


Fig. 3. Specific weight-moisture curve for groups

2-2-4- Compressive Strength Test

This test was conducted according ASTM C39 [28]. Cylindrical samples were placed between plates of the machine. Then vertical load was imposed until the fracture of the sample. This test was conducted on 7 and 28 day samples and also freeze-thaw samples.

2-2-5- Indirect Tensile Test

This test was conducted according Iran National Standard No. 6047 [29]. The aim of this test is determining the tensile strength of samples by splitting off the sample. In this test a diagonal compressive force is imposed along the length of the cylindrical sample until the fracture. It was conducted on 7 and 28-day samples with different percent of cement and NMP. Fig. 4 shows the test setup for compressive and indirect tensile strength.

2-2-6- Freezing and Thawing test

The samples were kept in a water basin for 14 days according to ASTM C192 [30] standard and then according to ASTM C666 they were placed in the refrigerator for 2 hours and 20 minutes at -18°C . Then they were placed in water with 20°C temperature to thaw. This process was done for 45 times. The period between freeze and thaw in a cycle should not exceed 10 minutes except when they are testing.



a) compressive strength



b) indirect tensile strength

Fig. 4. Loading method in the test

3. Results

The results of compressive and indirect tensile tests are given in Table 5. Table 6 shows the results of compressive test on 45 cycle of freeze-thaw and control samples.

Table 5. Result of Compressive and Indirect tensile tests

Material Type	Mix Design Name	Compressive Strength				Indirect Tensile Test			
		7 Day		28 Day		7 Day		28 Day	
		Mean Compressive Force (Ton)	Mean Compressive Strength (kg/cm ²)	Mean Compressive Force (Ton)	Mean Compressive Strength (kg/cm ²)	Mean Tensile Force (ton)	Mean Tensile Strength (kg/cm ²)	Mean Tensile Force (ton)	Mean Tensile Strength (kg/cm ²)
Group A	A-1	2.9	36.7	3.9	49.4	1.1	13.9	1.15	14.55
	A-2	4.9	62	6.1	77.25	1.4	17.7	1.4	17.7
	A-3	6	75.9	8.2	103.7	1.4	17.47	1.4	17.7
	A-4	3.6	45.5	5.4	68.4	1.1	13.9	1.15	14.55
	A-5	5	63.3	6.7	84.8	1.4	17.7	1.4	17.7
	A-6	6.3	79.7	8.6	108.95	1.4	17.7	1.45	18.35
Group B	B-1	2.2	27.8	2.95	37.3	1	12.7	1	12.7
	B-2	2.4	30.4	3.45	43.65	1	12.7	1	12.7
	B-3	3.5	44.3	4.9	62.05	1.1	13.9	1.1	13.9
	B-4	2.3	29.1	3.1	39.25	1	12.7	1.15	14.55
	B-5	3.1	39.2	3.8	48.1	1	12.7	1.1	13.9
	B-6	3.7	46.8	6.15	77.8	1.1	13.9	1.15	14.55
Group C	C-1	2.9	36.7	3.7	46.85	1.1	13.9	1.15	14.55
	C-2	3.8	48.1	4.6	58.25	1.1	13.9	1.15	14.55
	C-3	5	63.3	5.9	74.6	1.2	15.2	1.5	19
	C-4	3.1	39.2	3.8	48.1	1.1	13.9	1.15	14.55
	C-5	4.4	55.7	5.8	73.25	1.2	15.2	1.45	18.35
	C-6	5.2	65.8	6.05	76.55	1.6	20.3	1.6	20.3
Group D	D-1	2.8	35.4	3.85	48.75	1	12.7	1.2	15.2
	D-2	4.6	58.2	4.9	62	1.4	17.7	1.5	19
	D-3	5.2	65.8	6.35	80.4	1.5	19	1.6	20.3
	D-4	4	50.6	4.3	54.45	1.2	15.2	1.4	17.7
	D-5	4.8	60.8	6.7	84.8	1.4	17.7	1.5	19

D-6	5.8	77.1	6.75	85.45	1.5	19	1.6	20.3
-----	-----	------	------	-------	-----	----	-----	------

Table 6. results of compressive test on 45 cycle of freeze-thaw and control samples

Material Type	Mix Design Name	Average compressive strength of samples under freezing and thawing (kg/cm ²)	Compressive strength of control specimens (kg/cm ²)	Material Type	Mix Design Name (kg/cm ²)	Average compressive strength of samples under freezing and thawing (kg/cm ²)	Compressive strength of control specimens (kg/cm ²)
Group A	A-1	41.7	49.4	Group B	B-1	25.55	34.2
	A-2	65.85	77.2		B-2	34.2	48.1
	A-3	72.8	103.8		B-3	29.75	51.9
	A-4	44.95	68.4		B-4	29.1	38
	A-5	66.4	84.8		B-5	29.65	50.6
	A-6	79.75	108.9		B-6	45.6	75.9
Group C	C-1	25.3	49.4	Group D	D-1	23.45	46.8
	C-2	27.8	57		D-2	52.4	63.3
	C-3	41.75	65.8		D-3	51.9	97.7
	C-4	28.5	50.63		D-4	23.45	57
	C-5	46.85	59.5		D-5	54.45	83.6
	C-6	53.8	92.4		D-6	59.5	86

3-1- Results of Compressive Strength Test

As it is shown in Figs. 5 and 7, the compressive strength of the samples stabilized with NMP, in all groups is more than samples without NMP in both 7 and 28 day samples, but the percent of increase is different. Fig. 5 shows the effect of using NMP and cement on 7-day compressive strength, as can be seen, for 7-day strength, the maximum increase in strength is for groups A and D, and for the combination of 3% cement with 0.3% NMP. Also, For the group B and C the maximum increase of strength is for the combination of

6% cement with 0.6% NMP. However, in none of the groups, the sample with 12% cement and 1.2% NMP does not have the highest percentage increase in strength. Therefore, a high percent of cement and NMP will not necessarily lead to greater strength. Figs. 6 shows a comparison of the effect of adding cement and NMP separately for each group for the case where only cement is used and for the combination of cement and NMP.



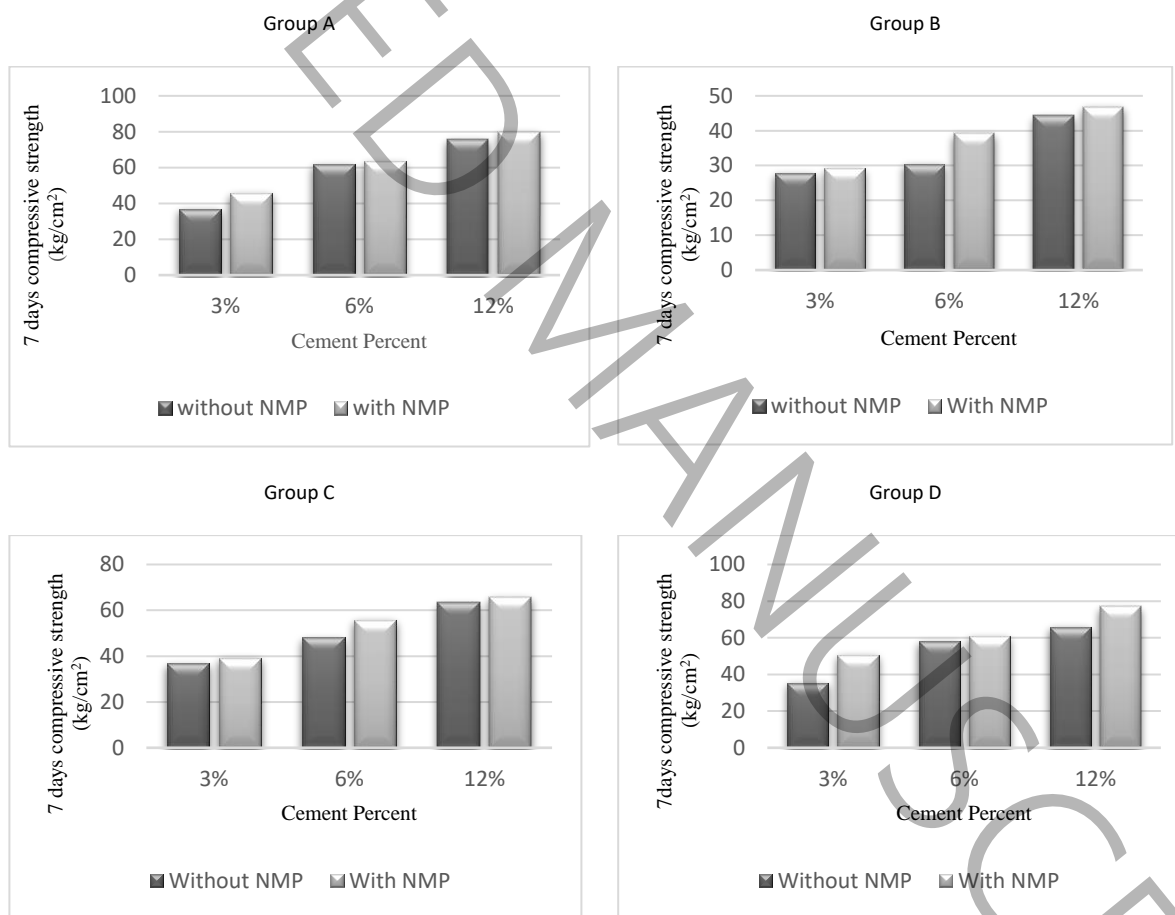


Fig. 5 Results of 7 day Compressive strength for each group of C&D Materials

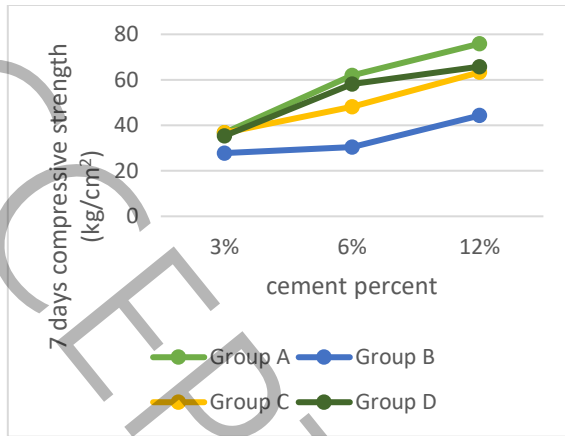

a) Stabilized only with cement and without NMP

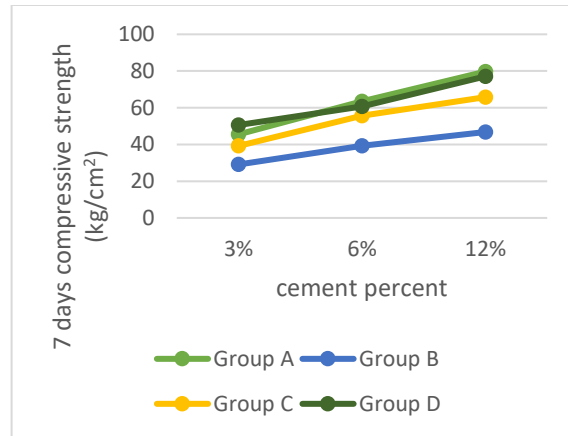

b) Stabilized with cement and NMP

Fig. 6. Results of the effect of cement, and cement with NMP, on 7-day compressive strength,

Fig. 7 shows the results of 28-day compressive strength on samples, as can be seen, for the 28-day condition, the highest increase in strength for group C and D is related to the case where 6% cement is mixed with 0.6% NMP. For group A, the maximum percentage of strength is related to the combination of 3% cement with 0.3% NMP. And for the group B, is related to the combination of 12% with 1.2% NMP. Figs. 8 shows the effect of only cement, and cement with NMP on increase of strength in each group.


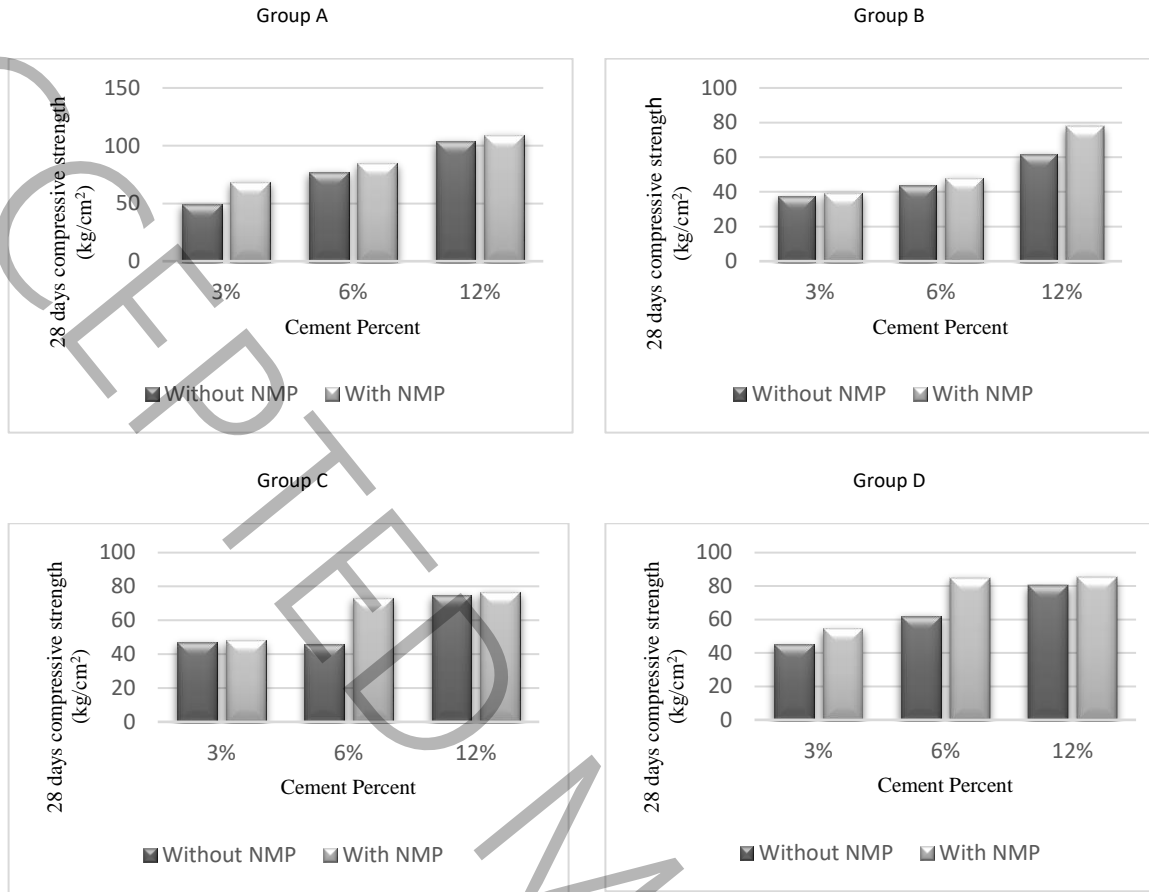


Fig. 7. Results of 28 day Compressive strength for each group of C&D Materials

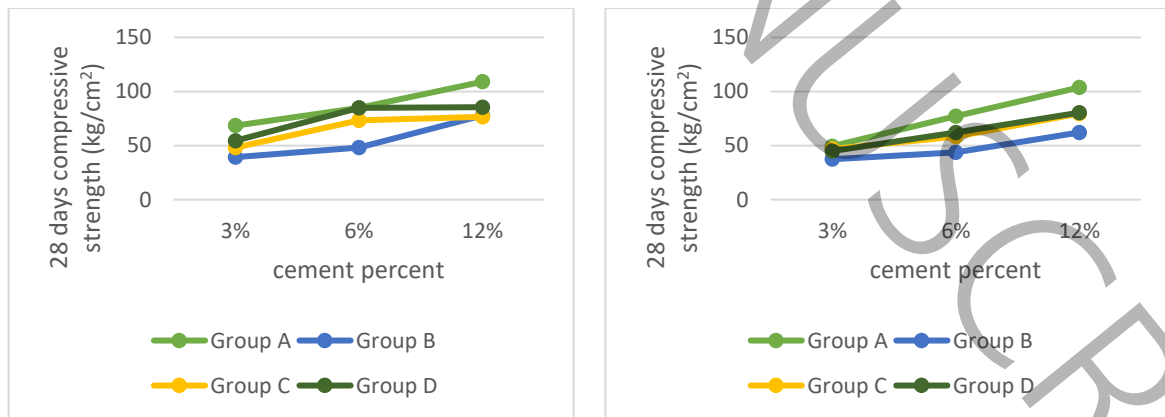


a) Stabilized only with cement and without NMP

b) Stabilized with cement and NMP

Fig. 8. Results of the effect of cement, and cement with NMP, on 28-day compressive strength

3-1-1- Comparison of 7-day and 28-day samples strength

The charts below show the increase of strength of the samples from 7 days to 28 days:

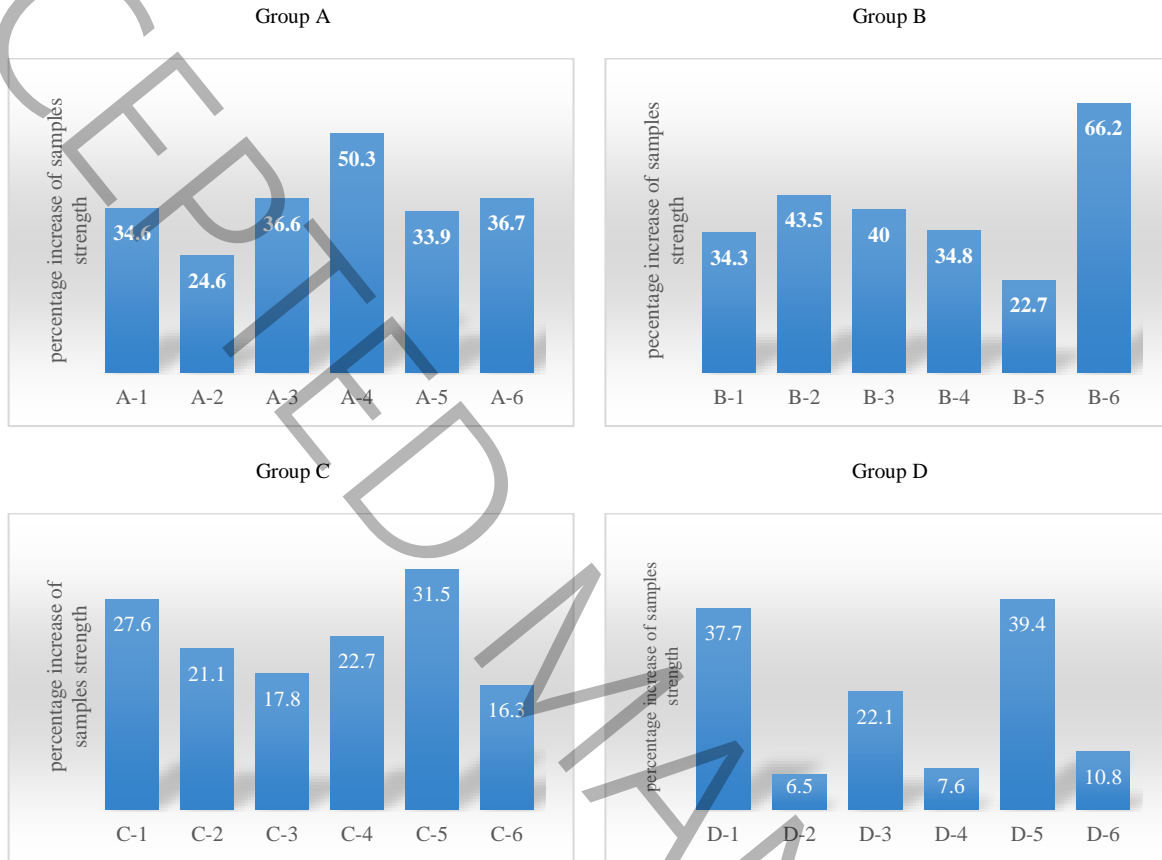

Figs. 9. samples strength increase from 7 days to 28 days for each group of materials

According to figs. 9, average increase in strength for materials for group A is 36.11%, for group B is 40.25%, for group C is 23.83, and for group D is 20.68. As it can be seen, the passage of time improves the resistance of all compounds containing cement and polymer, but these changes have reached their lowest value on average in the case of group D compounds which contain gypsum waste compounds, which can indicate an adverse effect. The presence of gypsum waste due to water absorption has affected the resistance change and reduced its increase. Especially in humidity above 6% where the effect of gypsum is more visible.

3-2- Results of Indirect Tensile strength

Figs. 10 shows the effect of NMP on 7-day indirect tensile strength separately for different groups. It can be seen that NMP did not change in most samples. However, in some cases, it has improved the tensile strength. NMP polymer for groups A and B did not change the tensile strength, or the effect was so small that it could not be recorded by the device. The maximum percentage of increase in tensile strength in samples is 33.5% relating to group C.



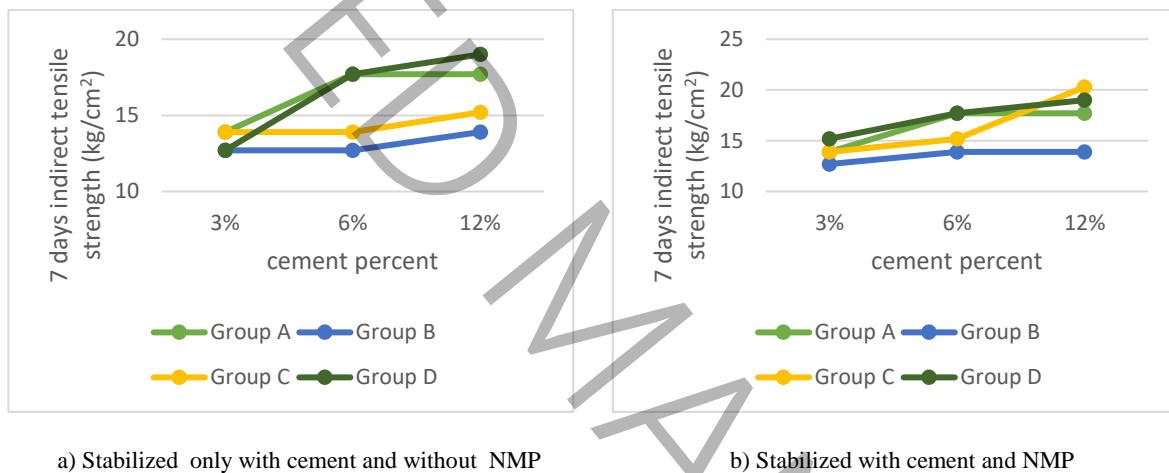


Fig. 10 Results of 7 day Indirect Tensile Strength (Kg/cm²)

Figs. 11 shows the effect of cement and polymer on 28-day tensile strength. As can be seen, the 28-day tensile strength of group B has the lowest value in all percentages. The addition of Nicoflok polymer has increased the position of group C materials to a higher strength than group A. Also, group D materials have the highest tensile strength, which can be the effect of the presence of gypsum in these materials.

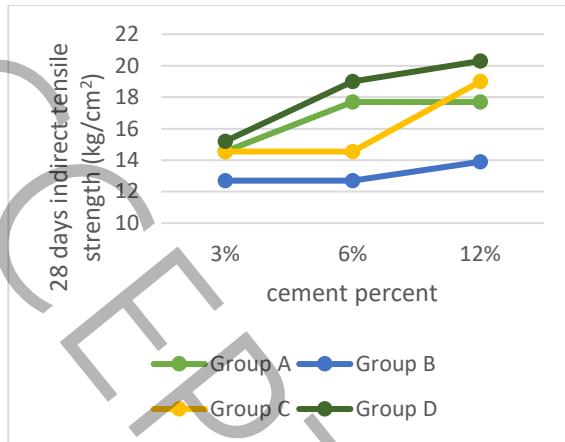

a) Stabilized only with cement and without NMP

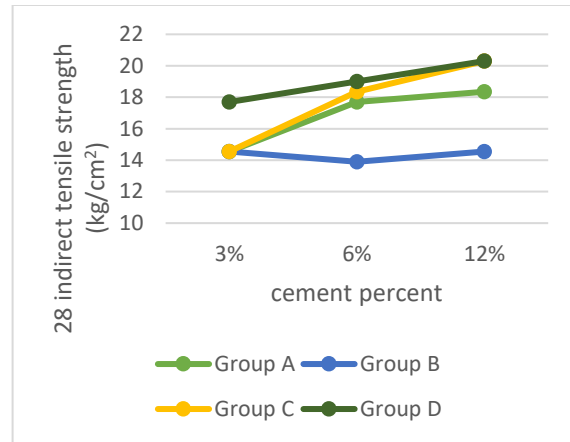

b) Stabilized with cement and NMP

Fig. 11. Results of 28 day Indirect Tensile Strength (Kg/cm²)

3-3- Results of 45 cycles of freezing and thawing test

The samples made for freezing and thawing test were subjected to 45 cycles of thawing and freezing after being curing in water for 14 days. According to figs. 12 and 13, the process of changing the compressive strength due to freezing and thawing test for different materials and different percentages of cement and NMP is different. The lowest drop in strength is related to group A with 6% of cement. Also, the maximum drop in strength is related to group D with 3% cement and 0.3% NMP. The lack of cement and polymer, which are among the materials, and the presence of gypsum waste, which is the most effective in reducing resistance during the time of melting and freezing, can be the reason for this decrease in resistance. In general, group A materials have more resistance against freezing and thawing.

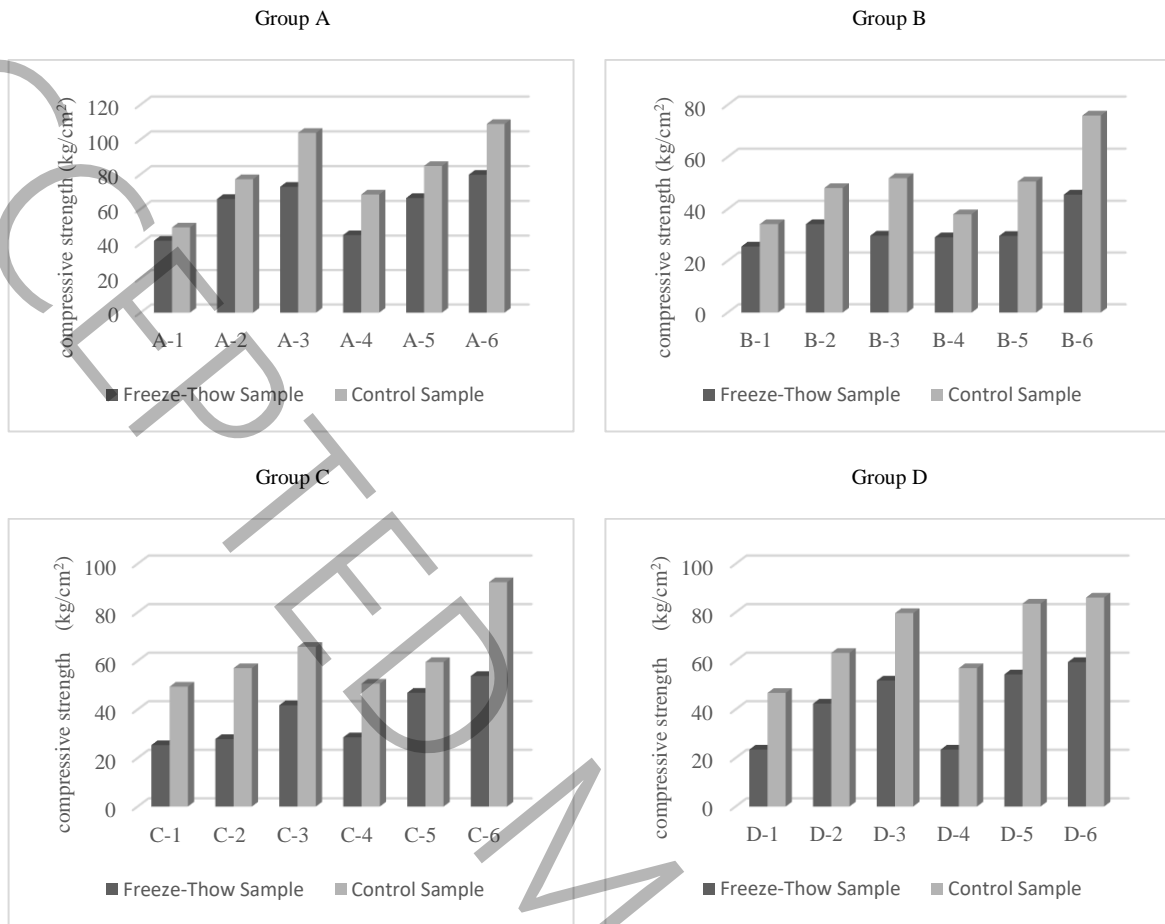


Fig. 12 Results of compressive test on samples with 45 cycles of freeze-thaw and also control samples

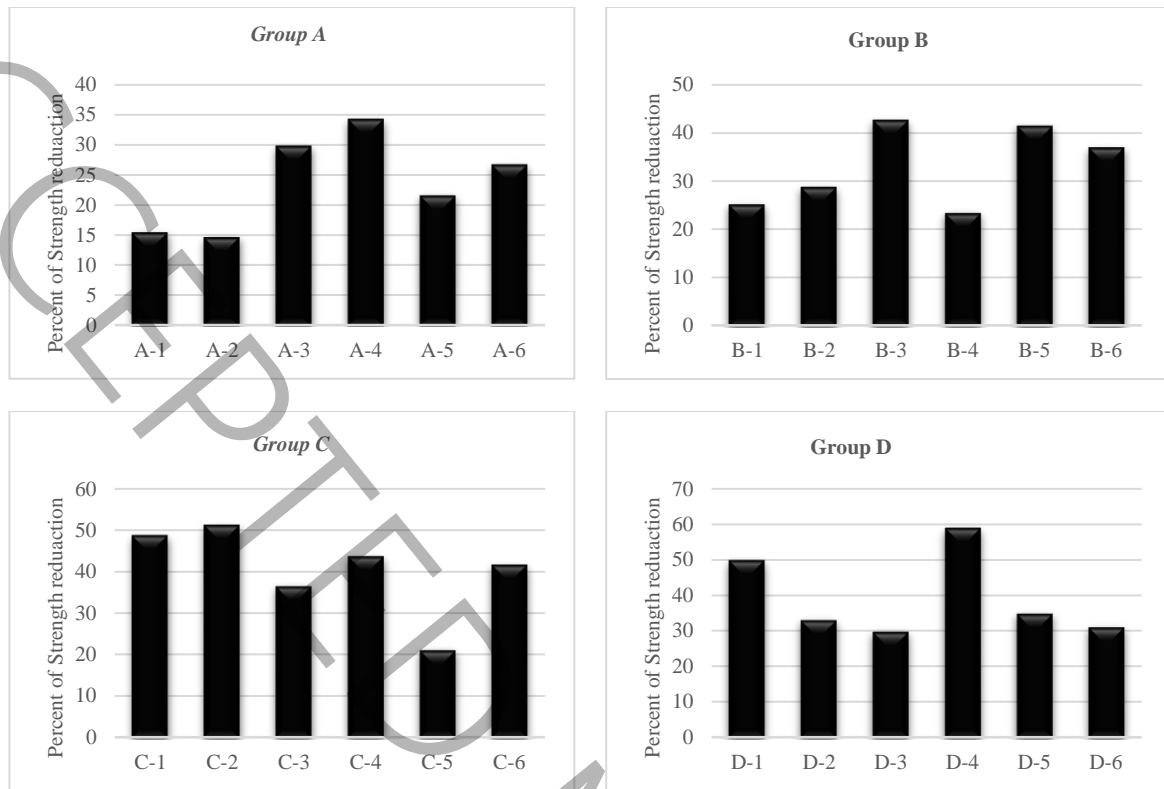


Fig. 13: Percent of strength reduction due to 45 cycles of freeze-thaw for each group of C&D materials

4. Conclusions

In this research, compacted samples of C&D wastes with 3, 6 and 12 percent cement and also samples with the same percentage of cement and 10% cement from NMP polymer were studied. Compressive, indirect tensile and freezing and thawing tests were performed on these samples. The results of the research are as follows:

- Considering the compaction curve, it can be concluded that materials of group A which contains cement and pieces of block and mortar, have more potential for compaction. The materials of group B have the lowest dry density at the same compaction energy.

- Adding gypsum to brick and cement waste causes an increase in the moisture content without decreasing dry density, which indicates that gypsum makes the mix absorb more water and that's why dry density of group D is more than group C's.
- Adding NMP causes increase in strength of 7 day samples of all groups and all percent. This increase from 2 to 42.9% is different for different percent. It can be said that it has increased 7-day strength of samples by 13.3% on average.
- It was seen that NMP was most effective in 3 and 6 percent of cement. In none of groups samples with 12% cement has more increase in strength. this shows that only using a lot of polymer and cement will not improve the condition.
- The most increase in 7-day strength in group C pertains to C-5 sample which contains 6% cement and 0.6% NMP. Adding gypsum waste causes the most increase in strength in group D pertains to D-4, i.e., for samples with 3% cement and 0.3% NMP indicates the positive effect of adding gypsum waste.
- Generally, it can be said that for 7-day samples, increasing cement and the NMP polymer weakens the effect of NMP.
- For the 28-day samples, in all percentages, the compressive strength of group B is lower than other groups, and the resistance of group C is between group A and B. the use of gypsum waste has improved the 28-day strength, but anyway, the strength of group A is higher than others.
- The average increase in 28-day sample strength which was the result of using NMP, was about 18.6%.
- For samples with 28 days curing, in all groups except B, samples with 3 and 6 percent cement have the highest increase in compressive strength due to use of NMP. The percent of increase in strength of samples with 28 days curing was 18.6% on average.

- In many 7 day samples NMP did not have any effect in increasing the strength in indirect tensile test or its effect was as low as that the machine was not able to record it. The average increase of 7-day strength for all groups is 6%.
- 7-day tensile strength of group B material has lowest value. Tensile strength of group C materials is between A and B in most cases. Adding gypsum to materials of group C results in an increase in the tensile strength.
- The presence of aggregates and primary granulation in group A materials has caused a high resistance in them, and the presence of cement even in cementation condition has also had an effect in creating this resistance.
- Generally, by increasing cement and NMP, their effect on 28-day strength decreases.
- The addition of gypsum wastes to the composition of group A and B scum has increased the percentage of moisture without reducing the dry specific weight, which can indicate that gypsum has absorbed more water in the composition, but because it is in the form of fine-grained material, it has caused the pores between the grains to be filled, and increased the specific dry weight compared to sample C.
- Increasing of tensile strength due to use of NMP means that using this polymer can decrease tensile cracks in pavements.
- Considering the obtained results, it can be seen that cement waste materials has usually better results in comparison to other wastes. But construction waste is commonly a combination of the aforementioned waste, mixing the materials according to group D will be the optimum state for pavement construction. Also the optimum percent for using of NMP is 6 percent cement and 0.6% NMP.

5. References

[1] o.g. kofoworola, sh, Etimation of construction waste generation and management in thiland, waste management, 29(2), (2008) 731-738.

- [2] v.b. schaefer, r, shrp 2 Geotechnical Solutions for Soil Improvement, Rapid embankment construction, and stabilization of the pavement working platform, National Concrete Pavement Technology Center, usa, 2014.
- [3] J.T.S. Dejong, K; Kavazanjian, E; Burns, S; Van, L. A, Biogeochemical processes and geotechnical applications: progress, opportunities and challenges, Bio- and Chemo-Mechanical Processes in Geotechnical Engineering, (2014) 287–301.
- [4] J.S.S. Tingle, R. L, Emulsion polymers for soil stabilization, Atlantic city, 2004.
- [5] F.M. Leite, R; Vasconcelos, k; Bernucci, L, Laboratory evaluation of recycled construction and demolition waste for pavements, Construction and Building Materials, (2011) 2972-2979.
- [6] M.S. Jain, Possible Ways of Re-Utilization of the Construction and Demolition Wastes in Various Construction Sectors, Sustain. Dev. Environ, (2019) 99-109.
- [7] A.P. Arulrajah, J; Ali, M; Bo, M, Geotechnical Properties of Recycled Concrete Aggregate in Pavement Sub-Base Applications, Geotechnical Testing Journal, 35(5), (2012) 743-751.
- [8] M.T. Contreras, S. R.; Lucas, M.C.; Lima, L. C. N.; Cardoso, D. S. L; Da Silva, G. A. C.; Dos Santos, A., Recycling of construction and demolition waste for producing new construction material (Brazil case-study), Construction and Building Materials, 123 (2016) 594-600.
- [9] H.K. Ulgol, A; Yildirim, G; Sahmaran, M; Aldemir, A; Figueira, D; Ashour, A, Mechanical and microstructural characterization of geopolymers from assorted construction and demolition waste-based masonry and glass, Journal of cleaner Production, 280 (2021).
- [10] S.E.K. Mousavi, A., Assessment of strength development in stabilized soil with CBR PLUS and silica sand, Journal of Traffic and Transportation Engineering (English Edition), 4(4) (2017) 412-421.
- [11] N.F.-J. Cristelo, A.; Vieira, C.; Miranda, T.; Palomo, A., Stabilisation of construction and demolition waste with a high fines content using alkali activated fly ash, Construction and Building Materials, 170 (2018) 26-39.
- [12] A.P. Arulrajah, S.; Wong, Y. C.; Maghool, F.; Horpibulsuk, S., Stabilization of PET plastic-demolition waste blends using fly ash and slag-based geopolymers in light traffic road bases/subbases, Construction and Building Materials, 284 (2021).
- [13] V.J. Gobieanandh, S, Evaluate the Strength of Cement Treated Recycled Construction and Demolition Aggregates as a pavement Materials, in: The 7th International Conference on Sustainable Built Environment, Kandy, Sri lanka, 2016.
- [14] O.F. Amo, A; Oke, B, Effect of eggshell powder on the stabilizing potential of lime on clay soil, International Journal of Natural and Applied Science, 3(3), (2007).
- [15] H.A.G. Ibrahim, Y.; Ng, Z. A.; Yap, S. P.; Mo, K. H.; Yuen, C. W.; Abutaha, F., Hydraulic and strength characteristics of pervious concrete containing a high volume of construction and demolition waste as aggregates, Construction and Building Materials, 253 (2020) 119-251.
- [16] M.v. parmenovich, S, Study of the effect of stabilizing additives on the properties of crushed stone-sand mixtures fortified with mineral binders, New Technologies, (2013).
- [17] N.K.N. Gusev, P. A, Study of Solidity of Road Structure Constructed with The Use of Polymer-Mineral Composition NMP, Bulletin of PSTU, 2, (2013) 52-58.
- [18] F.J.N. Rezie Moghaddam, B; Rezaie Moghaddam, T, Laboratory Investigation of the Effect of “NICOFLOK” Polymer on the Compressive and Tensile Strength of Desert and Coastal Sand at the pavement Layers, Amirkabir Journal Civil engineering, (2021).
- [19] I.B. Gavrilina, A, Analysis of Using Nicoflok Polymer-Mineral Additive for Replacing Stone Materials as Road Bases, IOP Conference Series: Materials Science and Engineering, (2018).
- [20] G.S. Moradi, S.; Katebi, H., Effect of Chemical and Biological Stabilization on the Resilient Modulus of Clay Subgrade Soil, International Journal of Pavement Research and Technology, (2021) 1-18.
- [21] M.R. Zirak Baroughi, A; Katebi, H, Influence of “Nicoflok” Polymer-Mineral with Portland Cement on Granular Soils and Recycled Asphalt Material, The baltic Journal of Road and Bridge Engineering, 15(5), (2020).
- [22] A.S. Ramezaniapour, M, Concrete Technology, Tehran, iust press, 2005.

- [23] h.R. sadeghi, S, Measurment of physical and chimical indicators of drinking water in ardabil, Journal of ardabil university of medical sciences, (2007).
- [24] ASTM E1621-13 Standard Guide for Elemental Analysis by Wavelength Dispersive X-Ray Fluorescence Spectrometry, in.
- [25] i.H.A.p.c.N. 234, 2nd edition, No. 101/88497, 2012.
- [26] S.T.M.f.R.o.C.t.R.F.a.T. ASTM C666, in, 2015.
- [27] A. D558, Standard Test Methods for Moisture-Density (Unit Weight) Relations of Soil-Cement MixturesASTM D558, 2019.
- [28] S.T.M.f.C.S.o.C.C.S. ASTM C39, 2014.
- [29] I. Number_6047, Evaluation direct Tensile Strength by Splitting Cylindrical Samples.
- [30] ASTM C192, Standard Practice for Making and Curing Concrete Test Specimens in the Laboratory, in, 2019.